

BS EN ISO 21179:2013



BSI Standards Publication

Light conveyor belts — Determination of the electrostatic field generated by a running light conveyor belt

National foreword

This British Standard is the UK implementation of EN ISO 21179:2013. It supersedes BS EN ISO 21179:2006 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/67, Conveyor belts.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013. Published by BSI Standards Limited 2013

ISBN 978 0 580 77362 4

ICS 53.040.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 April 2013.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Light conveyor belts - Determination of the electrostatic field generated by a running light conveyor belt (ISO 21179:2013)

Courroies transporteuses légères - Détermination du champ électrostatique engendré par une courroie transporteuse légère en marche (ISO 21179:2013)

This European Standard was approved by CEN on 2 March 2013.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 21179:2013) has been prepared by Technical Committee ISO/TC 41 "Pulleys and belts (including veebelts)" in collaboration with Technical Committee CEN/TC 188 "Conveyor belts" the secretariat of which is held by SNV.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2013, and conflicting national standards shall be withdrawn at the latest by September 2013.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 21179:2006.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 21179:2013 has been approved by CEN as EN ISO 21179:2013 without any modification.

Contents		Page
Foreword		iv
1	Scope	1
2	Normative references	1
3	Principle	1
4	Apparatus (see Figure 1).....	1
	4.1 Pair of pulleys, as follows:	1
5	Test piece	2
	5.1 Material	2
	5.2 Dimension	2
	5.3 Endless joining.....	2
	5.4 Conditioning.....	2
6	Procedure	3
7	Expression of results	5
8	Test report	5
Bibliography		6

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 21179 was prepared by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This second edition cancels and replaces the first edition (ISO 21179:2005), of which it constitutes a minor revision.

Light conveyor belts — Determination of the electrostatic field generated by a running light conveyor belt

1 Scope

This International Standard specifies a test method for the determination of the electrostatic field generated by a running light conveyor belt according to ISO 21183-1.

This dynamic procedure is required because the antistatic behaviour of light conveyor belts cannot in many cases be sufficiently described by measurement of the electrical resistances in accordance with ISO 21178.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable to its application. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 22, *Belt drives — Flat transmission belts and corresponding pulleys — Dimensions and tolerances*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

ISO 18573, *Conveyor belts — Test atmospheres and conditioning periods*

ISO 21181, *Light conveyor belts — Determination of the relaxed elastic modulus*

3 Principle

The test piece is run under specified conditions and produces an electrostatic field, the variation of which is recorded with time.

The test is carried out successively with both sides of the belt in contact with the pulleys.

4 Apparatus (see [Figure 1](#))

4.1 Pair of pulleys, as follows:

- a) electrically connected and earthed;
- b) made of steel;
- c) diameter 200 mm or larger, rim width 120 mm;
- d) raw, unplated surface roughness, maximum $Ra = 1,6 \mu\text{m}$, in accordance with ISO 4287;
- e) final coating of chromium plating;
- f) drive pulley, fixed, cylindrical;
- g) driven pulley moveable for tensioning, crowned in accordance with ISO 22 ($h = 0,6 \text{ mm}$).

4.2 Tensioning device, such that the test piece can be loaded according to the relevant $k_1 \%$ value given in [Table 1](#) to achieve uniform surface pressures.

Table 1 — Shaft load required

Modulus of elasticity k_1 % ^a N/mm	Shaft load F N
k_1 % $\leq 2,5$	50
$2,5 < k_1$ % ≤ 10	300
$10 < k_1$ % ≤ 30	900
k_1 % > 30	As per agreement
^a The value of k_1 % shall be established in accordance with ISO 21181.	

4.3 Drive, such that the belt runs directly from the drive pulley to the measuring device at a speed of 5 m/s.

4.4 Measuring device, either an electrostatic field meter with signal output that gives readings of the electrostatic field strength, E , in volts per metre, or a device that gives a direct reading of the surface potential, U , in volts.

4.5 Recording device, e.g. y/t recorder.

4.6 Means of correction for electrostatic fields

4.6.1 Earthed steel plate equipping the electrode, 200 mm $\times$ 200 mm, with the edges bent up with a radius of approximately 10 mm, to correct field distortion created by the measuring electrode. The lower surface of the electrode shall be flush with the lower surface of the steel plate. The size and shape of the perforation of the steel plate shall be adapted to the shape of the electrode used. The gap between the electrode and the steel plate shall not exceed 2 mm (see [Figure 1](#)).

4.6.2 Earthed steel plate, 600 mm $\times$ 200 mm, with the edges bent up with a radius of approximately 10 mm (see [Figure 1](#)), to shield the field to be measured from the field distortion generated by the return side of the test piece.

5 Test piece

5.1 Material

Test piece material shall be new, unused (“virgin”), but shall not be tested sooner than five days after manufacture. It shall be free from contamination and superficial damage.

5.2 Dimension

The test piece shall have an endless length of $(2\,500 \pm 50)$ mm and a width of (100 ± 1) mm.

5.3 Endless joining

The test piece shall be joined endlessly according to the manufacturer’s instructions.

5.4 Conditioning

Before testing, condition the test pieces in accordance with ISO 18573, Atmosphere B, for 24 h, except that for high-conductivity belts, the relative humidity may be reduced to (25 ± 5) %.

6 Procedure

Test conveyor belts which, due to their construction, require pulley diameters of more than 200 mm, with the smallest diameter possible and according to the manufacturer's instructions.

Measure the temperature and relative humidity in the test room.

Clean both pulleys (4.1) and, if necessary, remove any dust from the shielding steel plates (4.6.1 and 4.6.2).

After endlessly joining and conditioning of the test piece, install it on the testing apparatus with the normal running side in contact with the pulleys.

Tension the test piece in accordance with 4.2.

Install the recording device (4.5).

Position the measuring device (4.4) on the centre line of the test piece, 500 mm from the centre of the drive pulley, with a distance of 10 mm to 100 mm between the measuring device and the test piece surface not in contact with the pulley (see Figure 1).

NOTE Experience has shown that a distance of 25 mm is preferable.


Start the test piece and run it from the drive pulley (4.3) directly to the field measuring device.

Either record the electrostatic field strength, E , in volts per metre or, if the measuring device used gives a direct reading of the surface potential, U , record that value, in volts.

The measurement time shall be 30 min.

Repeat the same procedure with the other side of the belt in contact with the pulleys.

Dimensions in millimetres

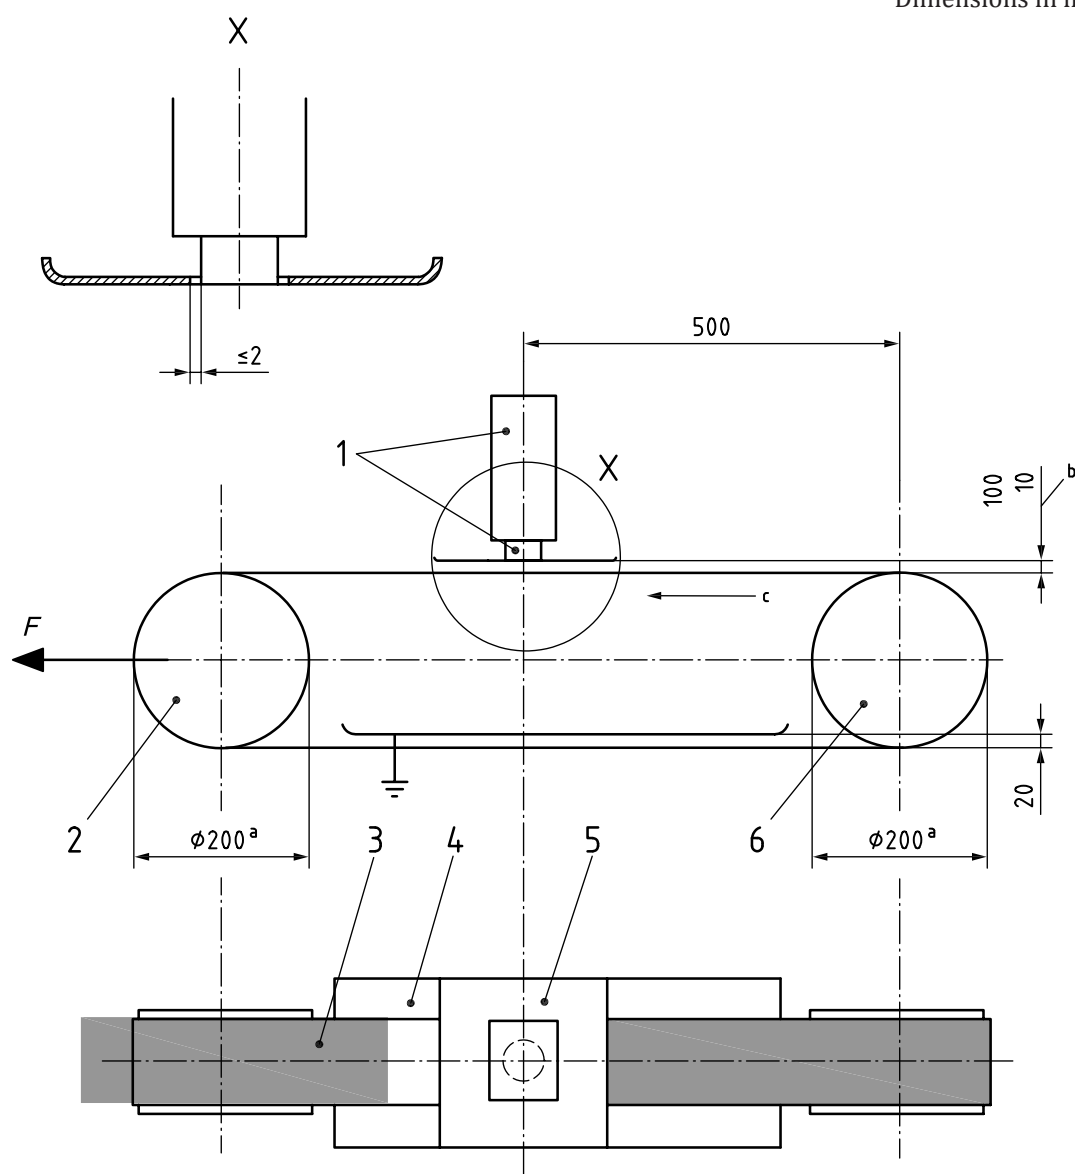

Key

- 1 measuring device with electrode
- 2 driven pulley, movable, crowned
- 3 test piece, endless $(2\,500 \pm 50) \text{ mm} \times (100 \pm 1) \text{ mm}$
- 4 earthed steel plate, $600 \text{ mm} \times 200 \text{ mm}$
- 5 earthed steel plate, $200 \text{ mm} \times 200 \text{ mm}$
- 6 drive pulley, fixed, cylindrical

a Diameter 200 mm or larger; see [Clause 6](#).

b Measuring distance of test piece surface not in contact with pulleys shall be between 10 mm and 100 mm.

c Direction of run.

Figure 1 — Basic arrangement of test bench for measurement of electrostatic field strength generated by running light conveyor belt

7 Expression of results

The two significant results within the test period shall be, firstly, the maximum value reached and, secondly, a value judged to be constant (i.e. when a change over the final 10 min is less than 10 %). Either the two values of these electrostatic field strengths shall be recorded or, if the measuring device used gives a direct reading of the surface potential, the two values of these surface potentials shall be recorded.

If the electrostatic field strengths are recorded, the surface potential, U , in volts, shall be calculated using the following formula:

$$U = E \times a$$

where a is the distance, in metres, between the measuring electrode and the conveyor belt surface.

These results are valid for virgin material according to [5.1](#).

If more than one measurement on one side is carried out (several measurements on one test piece or several test pieces), the arithmetic mean of the individual values either of E (calculated) or U (direct reading) shall be taken. All of the values shall be recorded.

8 Test report

The test report shall include the following information:

- a) complete designation of the tested conveyor belt material and date of manufacture;
- b) k_1 % value of the test piece(s);
- c) reference to this International Standard, i.e ISO 21179, and any necessary exceptions;
- d) places from which the test piece(s) were taken;
- e) test room temperature and relative humidity;
- f) conditioning period;
- g) the shaft load, in newtons;
- h) indication of belt side in contact with the pulleys;
- i) the values of U in accordance with [Clause 7](#);
- j) date of test.

Bibliography

- [1] ISO 21178, *Light conveyor belts — Determination of electrical resistances*
- [2] ISO 21183-1, *Light conveyor belts — Part 1: Principal characteristics and applications*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK



...making excellence a habit.™