

**BS EN ISO 21181:2013**



**BSI Standards Publication**

# **Light conveyor belts — Determination of the relaxed elastic modulus**

**National foreword**

This British Standard is the UK implementation of EN ISO 21181:2013. It supersedes BS EN ISO 21181:2006, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/67, Conveyor belts.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013.  
Published by BSI Standards Limited 2013.

ISBN 978 0 580 77364 8

ICS 53.040.10

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2013.

**Amendments issued since publication**

| Date  | Text affected |
|-------|---------------|
| <hr/> |               |

English Version

## Light conveyor belts - Determination of the relaxed elastic modulus (ISO 21181:2013)

Courroies transporteuses légères - Détermination du module d'élasticité relaxé (ISO 21181:2013)

This European Standard was approved by CEN on 12 February 2013.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

## Foreword

This document (EN ISO 21181:2013) has been prepared by Technical Committee ISO/TC 41 "Pulleys and belts (including veebelts)" in collaboration with Technical Committee CEN/TC 188 "Conveyor belts" the secretariat of which is held by SNV.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2013, and conflicting national standards shall be withdrawn at the latest by August 2013.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 21181:2006.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

### Endorsement notice

The text of ISO 21181:2013 has been approved by CEN as EN ISO 21181:2013 without any modification.

# Contents

Page

|                                                |           |
|------------------------------------------------|-----------|
| <b>Foreword</b>                                | <b>iv</b> |
| <b>Introduction</b>                            | <b>v</b>  |
| <b>1 Scope</b>                                 | <b>1</b>  |
| <b>2 Normative references</b>                  | <b>1</b>  |
| <b>3 Terms and definitions</b>                 | <b>1</b>  |
| <b>4 Symbols</b>                               | <b>2</b>  |
| <b>5 Principle</b>                             | <b>2</b>  |
| <b>6 Apparatus</b>                             | <b>2</b>  |
| <b>7 Test pieces</b>                           | <b>2</b>  |
| 7.1 Shape, dimensions, number and selection    | 2         |
| 7.2 Conditioning                               | 3         |
| <b>8 Procedure</b>                             | <b>3</b>  |
| <b>9 Calculation and expression of results</b> | <b>4</b>  |
| <b>10 Test report</b>                          | <b>6</b>  |
| <b>Bibliography</b>                            | <b>7</b>  |

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

ISO 21181 was prepared by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This International Standard is based on EN 1723:1999, prepared by CEN/TC 188.

This second edition cancels and replaces the first edition (ISO 21181:2005), of which it constitutes a minor revision.

## Introduction

Many applications for light conveyor belts require that the belt is initially tensioned and there is no subsequent change in belt length by adjustment of any rollers. In such cases, the tensioning force in the belt changes throughout the life of the belt because of two effects: permanent stretch and relaxation of the belt, both of which change its real elastic modulus. It is vital to have a means of establishing the way in which the tensioning forces change; and this test applies a cyclic stretching between two defined states of elongation over a large number of cycles. It has been found experimentally that the tensioning force drops in an exponential way. It is possible to measure the tensioning force and then to calculate what is defined in this International Standard as the “relaxed elastic modulus”. It is important to note that this is not a true elastic modulus, because it includes an element of permanent stretch; but, except in cases where the permanent stretch is relatively large, it is a measure of great practical value in determining final tensioning forces. This International Standard is designed to meet the requirements for such applications.





# Light conveyor belts — Determination of the relaxed elastic modulus

## 1 Scope

This International Standard specifies a test method for the determination of the relaxed elastic modulus of light conveyor belts according to ISO 21183-1 or other conveyor belts where ISO 9856 is not applicable.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

ISO 9856, *Conveyor belts — Determination of elastic and permanent elongation and calculation of elastic modulus*

ISO 18573, *Conveyor belts — Test atmospheres and conditioning periods*

ISO 21183-1, *Light conveyor belts — Part 1: Principal characteristics and applications*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **elastic modulus**

<conveyor belt technology> force per unit of width of a conveyor belt

Note 1 to entry: It is expressed in newtons per millimetre width of belt and is represented in ISO 9856 by the symbol  $M$ .

Note 2 to entry: This definition of the term deviates from that normally used in engineering, which is expressed in units of stress, i.e. a force per unit of cross-section, and represented by the symbol  $E$  (see, for example, ISO 527-4).

### 3.2

#### **elastic modulus**

<light conveyor belt technology> force in newtons per unit of width required to extend a representative test piece of light conveyor belting by 1 % of its original length

Note 1 to entry: The force is represented by the symbol  $k$  and, consequently, the elastic modulus is represented by the symbol  $k_{1\%}$ . This value is also called the “tensile force for 1 % elongation per unit of width” or “ $k_{1\%}$  value”. It is expressed in newtons per millimetre.

Note 2 to entry: In EN 10002-1:2001, the symbol  $k$  is used to represent the coefficient of proportionality.

### 3.3

#### **relaxed elastic modulus**

<light conveyor belt technology> elastic modulus of a light conveyor belt after being cycled between predetermined limits of extension for 500 cycles

Note 1 to entry: The  $k_{1\%}$  value of a new conveyor belt is higher than that of a used conveyor belt in which relaxation has taken place in service. The relaxation takes place following an exponential function.

## 4 Symbols

For the purposes of this document, the following symbols apply.

|              |                                                                                                           |
|--------------|-----------------------------------------------------------------------------------------------------------|
| $F_A, F_B$   | are the maximum and minimum tensile forces, respectively, in the test piece, in newtons;                  |
| $F'_A, F'_B$ | are the specific values of $F_A, F_B$ referred to the width of the test piece, in newtons per millimetre; |
| $a$          | is the value, in newtons per millimetre, of $k_{1\%}$ for $z = 1$ ;                                       |
| $b$          | is the manufactured width of conveyor belt, in millimetres;                                               |
| $r$          | is the correlation coefficient;                                                                           |
| $x$          | is the variable in equation of straight line;                                                             |
| $y$          | is the value of equation of straight line;                                                                |
| $z$          | is the number of cyclic elongations.                                                                      |

## 5 Principle

A test piece is exposed to a cyclic elongation between two defined limits and the tensile force recorded as a function of the number of cycles. From that graph, the relaxed elastic modulus is determined by calculation through a logarithmic regression.


## 6 Apparatus

**6.1 Tensile testing machine**, capable of applying a load suitable for the strength of the test piece and with a force measuring system in accordance with ISO 7500-1:2004, class of machine 3 or better (e.g. class of machine 2), and also capable of applying the load in displacement-controlled cycles of  $\pm 5$  mm and with a frequency of 0,5 Hz (this frequency being realizable also with older, mechanically controlled dynamometers).

## 7 Test pieces

### 7.1 Shape, dimensions, number and selection

Cut from the full thickness of the conveyor belt in the longitudinal direction five rectangular test pieces each  $(50 \pm 0,5)$  mm wide and having a length of 500 mm plus twice the length necessary for clamping in the jaws. Select the test pieces from the conveyor belt in accordance with [Figure 1](#). The test piece shall not be tested sooner than five days after manufacture.

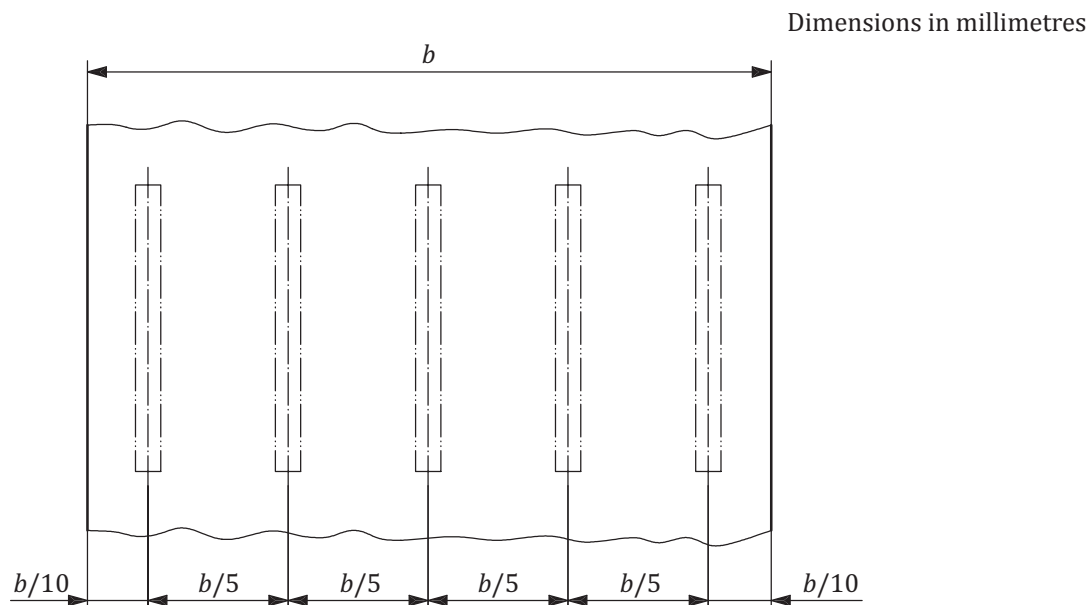

**Figure 1 — Distribution of test piece selection**

## 7.2 Conditioning

Before testing, condition the test pieces in accordance with ISO 18573, Atmosphere B, for 24 h, except that, if the light conveyor belt (as specified in ISO 21183-1 ) consists of materials with a high absorption of moisture, e.g. cotton or polyamide, condition the test piece for 48 h.

## 8 Procedure

Place the ends of the test piece between the jaws of the tensile testing machine (6.1) such that the test piece is straight without using force. Ensure that the free length between the jaws is  $500 \text{ mm} \pm 1 \text{ mm}$  and that there is no slippage of the test piece in the jaws during the test.


Slippage can be minimized by rubbing rosin on the portion of the test piece that will be in the jaws, removing any excess rosin and enclosing both sides of the rosin-coated test piece with coarse emery cloth. The emery cloth should be folded over the ends of the test piece with the coarse side of the cloth next to the rosin-coated surfaces.

Elongate the test piece cyclically, either

- a) between 1 % and 2 % (5 mm and 10 mm) at a frequency of 0,5 Hz, or
- b) if the conveyor belt contains reinforcing elements with a high elastic modulus (e.g. with reinforcing elements of aramid threads), between 0,5 % and 1 % (2,5 mm and 5 mm) at the same frequency of 0,5 Hz.

**NOTE** For a), the same effect will be realized if the test piece is given an initial elongation of 1,5 %, corresponding to 7,5 mm, and a cyclic alteration of the elongation of  $\pm 0,5 \%$ , corresponding to  $\pm 2,5 \text{ mm}$ , is superposed at the same frequency. The average speed of deformation in the test piece will be  $5 \text{ mm/s}$  ( $= 300 \text{ mm/min}$ ).

Record the tensile force during 500 cyclic elongations as a function of the number of cycles. At the end of the test, measure the permanent elongation by reducing the tensioning force to zero and measuring the distance between the jaws. If this elongation is equal to or exceeds 1 % of the initial length, this indicates that the method is unsuitable for such a belt type; in which case, use the method according to ISO 9856 instead.

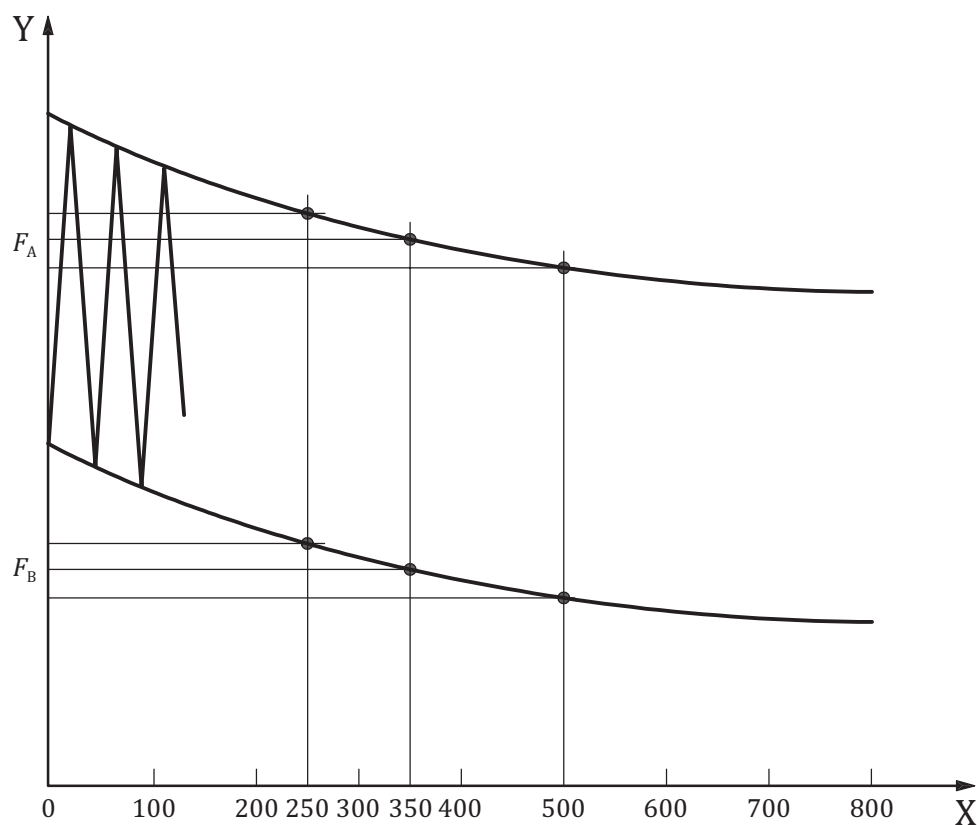

#### Key

X number of cycles,  $z$   
Y tensile force,  $F$ , N

**Figure 2 — Tensile force as function of number of cyclic elongations**

## 9 Calculation and expression of results

Read the forces  $F_A$  and  $F_B$  for the number of cyclic elongations  $z = 250$ ,  $z = 350$ , and  $z = 500$  from the graph shown in [Figure 2](#).

Divide all of these forces by belt width (50 mm) to give the elastic moduli, as follows:

$$F'_A = \frac{F_A}{50} \text{ N/mm} \quad (1a)$$

$$F'_B = \frac{F_B}{50} \text{ N/mm} \quad (1b)$$

If a cyclic elongation between 1 % and 2 % has been applied, calculate the elastic modulus from the following formula:

$$k_{1\%} = \frac{F'_A + F'_B}{2 \times 1,5} \text{ N/mm} \quad (2)$$

If a cyclic elongation between 0,5 % and 1 % has been applied, calculate the elastic modulus from the following formula:

$$k_{1\%} = \frac{F'_A + F'_B}{2 \times 0,75} \text{ N/mm} \quad (3)$$

From the three calculated  $k_{1\%}$  values and the corresponding number of cyclic elongations, determine the equation of a straight line of the form:

$$y = a + cx \quad (4)$$

and subsequently carry out a logarithmic regression.

For that, use a calculator which provides statistical functions. The  $x$ -values of the number couples to enter are the numbers of cyclic elongations given as natural logarithms ( $\ln z$ ). The  $y$ -values are the corresponding calculated  $k_{1\%}$  values.

Therefore, Formula (4) becomes:

$$k_{1\%} = a + (c \times \ln z) \quad (5)$$

where

$c$  is the slope of the straight line;


$a$  is  $k_{1\%}$  for  $z = 1$ .

Determine both values and the correlation coefficient,  $r$ , by calculator.

The correlation coefficient  $r$  of the straight line should be as high as possible. Ideally, it would be 1,0, although values between 0,8 and 1,0 are sufficiently high. If  $r < 0,7$ , the test should be repeated and the calculation carried out with larger numbers of cyclic elongations,  $z$ .

By means of the found values for  $a$  and  $c$  and with Formula (5), calculate the relaxed  $k_{1\%}$  value by putting in a value for  $z$  of 43 200 cyclic elongations, corresponding to a testing time of 24 h at a frequency of 0,5 Hz (see [Figure 3](#)). (Numerically,  $\ln 43\,200 = 10,67$ .)

Calculate the individual relaxed  $k_{1\%}$  values for all five test pieces and determine the arithmetic mean of the five values.

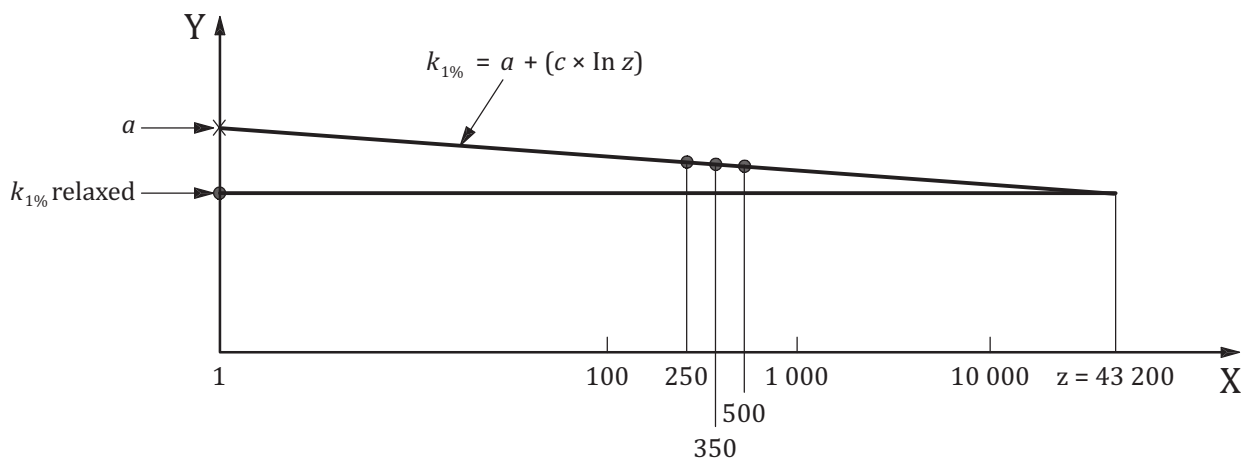

#### Key

- X  $\ln z$  (-)  
Y  $k_{1\%}$ , N/mm  
 $a$   $k_{1\%}$  for  $Z = 1$

**Figure 3 — Determination of relaxed  $k_{1\%}$  value**

## 10 Test report

The test report shall include at least the following information:

- a complete designation of the tested conveyor belt material and the manufacturing date;
- reference to this International Standard, i.e. ISO 21181;
- test room temperature and relative humidity;
- conditioning period;
- procedure applied (elongation between 1 % and 2 % or between 0,5 % and 1 %);
- results of the test, in accordance with [Clause 9](#);
- date of the test.

## Bibliography

- [1] ISO 527-4, *Plastics — Determination of tensile properties — Part 4: Test conditions for isotropic and orthotropic fibre-reinforced plastic composites*
- [2] EN 10002-1:2001, *Metallic materials — Tensile testing — Part 1: Method of test at ambient temperature*







# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK



...making excellence a habit.™